



REPORT

Testing coated samples with COT sample number 05-11-20/0514 and 19-07-21/0326 according to ISO 12944-6 Im2/3 Very High

Haarlem, 11th of February 2022

Consultancy Laboratory

Jan Tademaweg 40
2031 CV Haarlem
P.O. Box 2113
2002 CC Haarlem
The Netherlands
T +31 23-5319544
F +31 23-5277229
E info@cot-nl.com
I www.cot-nl.com

Client : ZINGAMETALL BVBA
Industriepark - Rozenstraat 4
B - 9810 Eke
Belgium
Contact person: Mr. P. Claeys

Specified system	coat	Product name	nDFT
	1 st coat	Zinga	60 µm
	2 nd coat	Zingatarfree	90 µm
	3 rd coat	Zingatarfree	90 µm
	Total		240 µm

Project number : 20200273

Report number : LAB22-0032-REP Rev. 1

Handled by : Ms. F.F. Sudarso

Conclusion

The coated samples of reference adhesion and immersion with COT sample number **05-11-20/0514 and** neutral salt spray **19-07-21/0326** meet the requirements of ISO 12944-6 Im2/3 Very High.



CONTENTS

1	INTRODUCTION	3
1.1	Order.....	3
1.2	General information.....	3
1.3	Information received from the client.....	3
2	PROCEDURE	4
2.1	Determination of the dry film thickness using a magnetic induction gauge, ISO 17025 Scope number 1 (Q).....	4
2.2	Adhesion.....	4
2.3	Pull-of adhesion according to ISO 4624 Method B.....	4
2.4	Determination of the resistance against corrosion in artificial atmospheres, Neutral salt spray, ISO 17025 Scope number 4 (Q).....	4
2.5	Immersion test.....	5
3	REQUIREMENTS	5
3.1	Reference adhesion before tests.....	5
3.2	Assessment after Neutral Salt Spray test.....	5
3.3	Assessment after Immersion test.....	5
4	RESULTS.....	7
4.1	Dry film thickness.....	7
4.2	Assessment before tests.....	7
4.3	Assessment after Neutral Salt Spray test.....	8
4.4	Assessment after 5% NaCl immersion test.....	8
5	SUMMARY.....	9
6	CONCLUSION.....	9

ANNEX Photographs

Revision 1: - Corrected: - Product name
- DFT Panel 21/326-2, Panel 21/326-2 and Panel 21/326-2
- Adhesion date on assessment after 5% immersion test
- In the conclusion: ISO 12944-6 Im2/3 High to Very High

INTRODUCTION

1.1 Order

At the request of Zingametall BVBA in Eke, Belgium, the Centrum voor Onderzoek en Technisch advies (COT bv) in Haarlem, The Netherlands, has tested the samples with COT sample number 05-11-20/0514 and 19-07-21/0326 according to ISO 12944-6 Im2/3 Very High.

With reference number RB/MH LAB20-0395-OFF-Revision 1, dated 7th October 2020.

Tests marked with 'Q' are under accreditation according to ISO/IEC 17025 with registration number L535.

1.2 General information

Table 1: Received samples

COT sample number	Sample	Received
05-11-20/0514	12x Coated steel panels, dimensions 75 x 150 x 5 mm, labelled* Pull off: 1, 10 and 12/ NSS: 11, 13 and 18/ Con : 5, 18! and 20/ IMM : 2, 8 and 14	5-11-2020
19-07-21/0326	3x Coated steel panels, dimensions 75 x 150 x 5 mm, labelled*: 2, 3 and 5	19-7-2021

*) Labelled by the client.

The coating system has been applied to the test panels by the client.

1.3 Information received from the client

Substrate

Mild steel panels.

Surface preparation

Blasted to Sa 2.5 grade cleanliness according to ISO 8501-1.

Surface roughness Medium (G) according to ISO 8503-1.

Coating system build up and specified dry film thickness

Zinga : 60 µm

Zingatarfree : 90 µm

Zingatarfree : 90 µm

Total nominal dry film thickness (nDFT) : 240 µm

Test specification : ISO 12944-6

Corrosivity category : Im2/3

Durability range : Very High

2 PROCEDURE

2.1 Determination of the dry film thickness using a magnetic induction gauge, ISO 17025 Scope number 1 (Q)

Before starting the tests the total dry film thickness of the coating system has been measured according to ISO 2808:7C, COT Instruction 30.01.12-2 with a magnetic dry film thickness meter (COT E004) and corrected for surface roughness (C = correction value) according to ISO 19840. On each panel 5 measurements have been carried out.

2.2 Adhesion

Before adhesion testing the panels have been conditioned for 7 days at 23 ± 2 °C and 50 ± 5 % R.H., the test has been performed under the same conditions. All individual values have been reported.

Depending on the uncorrected mean DFT of the coating system, the following methods are used:

- If lower or equal to 250 micrometers: cross-cut method according to ISO 2409,
- If higher than 250 micrometers: pull-off method B according to ISO 4624.

2.3 Pull-of adhesion according to ISO 4624 Method B

On each panel three trials have been performed.

The adhesion of the coating system has been determined by an automatic hydraulic adhesion tester (COT A004/A012) in accordance with ISO 4624 Method B. The coating surface and the dolly (diameter 20 mm) have been sanded lightly and the epoxy adhesive has been applied. After curing of the adhesive and prior to testing, the coating and the adhesive have been scribed around the dolly down to the bare metal.

The fractures of the adhesion test have been evaluated according to this scheme:

- A/B Fracture between the steel surface and 1st coat (adhesion failure).
- B Fracture in the 1st coat (cohesion failure).
- B/C Fracture between the 1st and 2nd coat (adhesion failure).
- C Fracture in the 2nd coat (cohesion failure).
- C/D Fracture between the 2nd and 3rd coat (adhesion failure).
- D Fracture in the 3rd coat (cohesion failure)
- /Y Fracture between the outer coat and the glue (adhesive failure).

2.4 Determination of the resistance against corrosion in artificial atmospheres, Neutral salt spray, ISO 17025 Scope number 4 (Q)

Resistance to Neutral Salt Spray (NSS) has been tested in accordance with ISO 9227 NSS, COT Instruction 30.01.27-1 on three test panels. The fully cured coating system has been scribed horizontally down to the steel substrate, the scribe line being 2 mm wide and 50 mm long.

General data

Apparatus number	:	COT S008
Type of water	:	Demineralised water (< 1 µS)
Salt	:	Sodium chloride (NaCl) p.a.
Test temperature	:	35 ± 2 °C
Collected salt solution	:	1.0 – 2.0 ml/hour/80 cm ²
pH of the collected salt solution	:	6.5 – 7.2
Salt concentration of the collected solution	:	50 ± 5 g/l
Exposition angle	:	approx. 20 ° from the vertical
Test duration	:	2160 hours

Immediately after exposure the panels were evaluated for visual surface defects according to ISO 4628-2, -3, -4 and -5.

The corrosion at the scribe has been determined within 8 hours after the end of the exposure. The corrosion at the scribe is calculated from the equation: $M=(C-W)/2$, where

M = corrosion creep (mm)

C = average of the nine measurements (mm)

W = the original width of the scribe (mm)

After the assessments photos have been taken (See Annex).

2.5 Immersion test

Three test panels have exposed to immersion testing according to ISO 2812-2 using sodium chloride, 5 % (mass fraction) aqueous solution (instead of water) for 4000 hours. The panels without scribe line shall be partially immersed in the test medium.

Immediately after exposure the panels were evaluated for visual surface defects according to ISO 4628-2, -3, -4 and -5.

Adhesion by pull-off method has been tested after at minimum 7 days acclimation.

3 REQUIREMENTS

Only one of the three panels shall be allowed not to comply with the requirements.

3.1 Reference adhesion before tests

Table 2: Adhesion before tests

Adhesion ISO 4624		Requirements
ISO 4624	Individual values	≥ 2.5 MPa
	Break Area	No adhesive failure between steel or metalized steel and the first coat unless ≥ 5 MPa

3.2 Assessment after Neutral Salt Spray test

Table 3: Assessment after Neutral Salt Spray test

Neutral salt spray ISO 9227- 5.2 NSS, 2160 hours (ISO 17025 Scope number 4)		Requirements
ISO 4628-2	Blistering	0(S0)
ISO 4628-3	Rusting	Ri 0
ISO 4628-4	Cracking	0(S0)
ISO 4628-5	Flaking	0(S0)
Corrosion from scribe		≤ 1.5 mm
ISO 4624	Individual values	≥ 2.5 MPa
	Break Area	No adhesive failure between steel or metalized steel and the first coat unless ≥ 5 MPa

3.3 Assessment after Immersion test

Table 4: Assessment after Immersion test



Immersion		Requirements
ISO 12944-6, 4000 hours		
ISO 4628-2	Blistering	0(S0)
ISO 4628-3	Rusting	Ri 0
ISO 4628-4	Cracking	0(S0)
ISO 4628-5	Flaking	0(S0)
ISO 4624	Individual values	≥ 2.5 MPa
	Break Area	0% adhesive failure between steel or metalized steel and the first coat unless ≥ 5 MPa



4 RESULTS

4.1 Dry film thickness

Table 5: Dry film thickness test panels (ISO 17025 Scope number 1).
Test date: 27-7-2020 (panel 05-11-20/0514) and 15-11-2021(panel 19-07-21/0326)

Q	Dry film thickness ISO 19840 (C = 25 µm)	COT sample number				
		05-11-20/0514 and 19-07-21/0326				
		Panel 0514-1(1)	Panel 0514-2(10)	Panel 0514-3(12)	Panel 0326-2	Panel 0326-3
	Readings (n=5)	236 235 291 275 244	312 301 326 298 278	233 255 263 233 231	246 234 233 236 232	246 238 254 249 236
	Min. - Max. (µm) Average, SD (µm)	235 - 291 256 ± 25	278 - 326 303 ± 18	231 - 263 243 ± 15	232 - 246 236 ± 6	236 - 254 245 ± 8
		Panel 0326-5	Panel 0514-7(5)	Panel 0514-8(18!)	Panel 0514-9(20)	Panel 0514-10(2)
	Readings (n=5)	242 246 242 245 260	242 247 271 260 240	243 266 297 264 256	231 223 257 221 206	268 265 294 300 286
	Min. - Max. (µm) Average, SD (µm)	242 - 260 247 ± 7	240 - 271 252 ± 13	243 - 297 265 ± 20	206 - 257 228 ± 19	265 - 300 283 ± 16
		Panel 0514-11(8)	Panel 0514-12(14)			
	Readings (n=5)	292 240 298 284 274	244 211 283 265 256			
	Min. - Max. (µm) Average, SD (µm)	240 - 298 278 ± 23	211 - 283 252 ± 27			

4.2 Assessment before tests

Table 6: Reference Assessment of coating adhesion. (ISO 17025 scope No. 3)
Test date : 15-11-2021

Q	Reference Adhesion ISO 4624 Pull-off test ISO 2409 cross-cut test	COT sample number		
		05-11-20/0514 and 19-07-21/0326		
		Panel 0514-1(1)	Panel 0514-2(10)	Panel 0514-3(12)
	ISO 4624 Adhesion (MPa),	6.8	7.7	7.5
	Break area (%)	100% D	100% D	100% D
		6.3 100% D	6.7 100% D	7.8 100% D
		7.8 100% D	8.2 100% D	7.8 100% D

4.3 Assessment after Neutral Salt Spray test

Table 7: Assessment after Neutral Salt Spray test. (ISO 17025 scope No. 4)

Test date : 29-07-2021 until 27-09-2021, adhesion 15-11-2021

Q	Neutral Salt Spray ISO 9227-5.2 NSS Exposure 2160 hours	COT sample number 05-11-20/0514 and 19-07-21/0326		
		Panel 0326-2	Panel 0326-3	Panel 0326-5
Q	ISO 4624-2 Blistering	0(S0)	0(S0)	0(S0)
Q	ISO 4624-3 Rusting	Ri 0	Ri 0	Ri 0
Q	ISO 4624-4 Cracking	0(S0)	0(S0)	0(S0)
Q	ISO 4624-5 Flaking	0(S0)	0(S0)	0(S0)
	Corrosion from scribe (mm)	0.8	0.6	0
	ISO 4624 Adhesion (MPa)	4.1	4.5	4.8
	Break area (%)	100% B	100% B	100% B
		4.8	4.8	3.4
		100% B	100% B	100% B
		5.3	5.3	3.2
		100% B	100% B	100% B

4.4 Assessment after 5% NaCl immersion test

Table 8: Assessment after 5% NaCl immersion test 4000 hours.

Test date : 20-11-2020 until 5-05-2021, adhesion 14-06-2021

	Immersion ISO 2812-2, 5% NaCl Exposure 4000 hours	COT sample number 05-11-20/0514 and 19-07-21/0326		
		Panel 0514-10(2)	Panel 0514-11(8)	Panel 0514-12(14)
Q	ISO 4624-2 Blistering	0(S0)	0(S0)	0(S0)
Q	ISO 4624-3 Rusting	Ri 0	Ri 0	Ri 0
Q	ISO 4624-4 Cracking	0(S0)	0(S0)	0(S0)
Q	ISO 4624-5 Flaking	0(S0)	0(S0)	0(S0)
	ISO 4624 Adhesion (MPa)	3.3	5.1	4.5
	Break area (%)	90% B, 10% B/C	60% B, 40% C	90% B, 10% B/C
		7.3	8.1	6.6
		100% C	100% C	100% C
		5.2	6.8	5.3
		100% C	100% C	100% C

5 SUMMARY


Table 9: Summary of the test results (COT sample number **05-11-20/0514** and **19-07-21/0326**)

Test method	Test duration	Pass / Fail
Reference adhesion	N.A.	Pass
Neutral salt spray test ISO 6270-1 (ISO 17025 scope number 4)	2160 hours	Pass
Immersion ISO 12944-6	4000 hours	Pass

6 CONCLUSION

The coated samples of reference adhesion and immersion with COT sample number **05-11-20/0514** and Neutral salt spray **19-07-21/0326** meet the requirements of ISO 12944-6 Im2/3 Very High.

CENTRUM VOOR ONDERZOEK
EN TECHNISCH ADVIES (COT bv)



F. F. Sudarso
Laboratory Technician



M.P. de Haan
Technical Manager Laboratory

ANNEX

Photographs


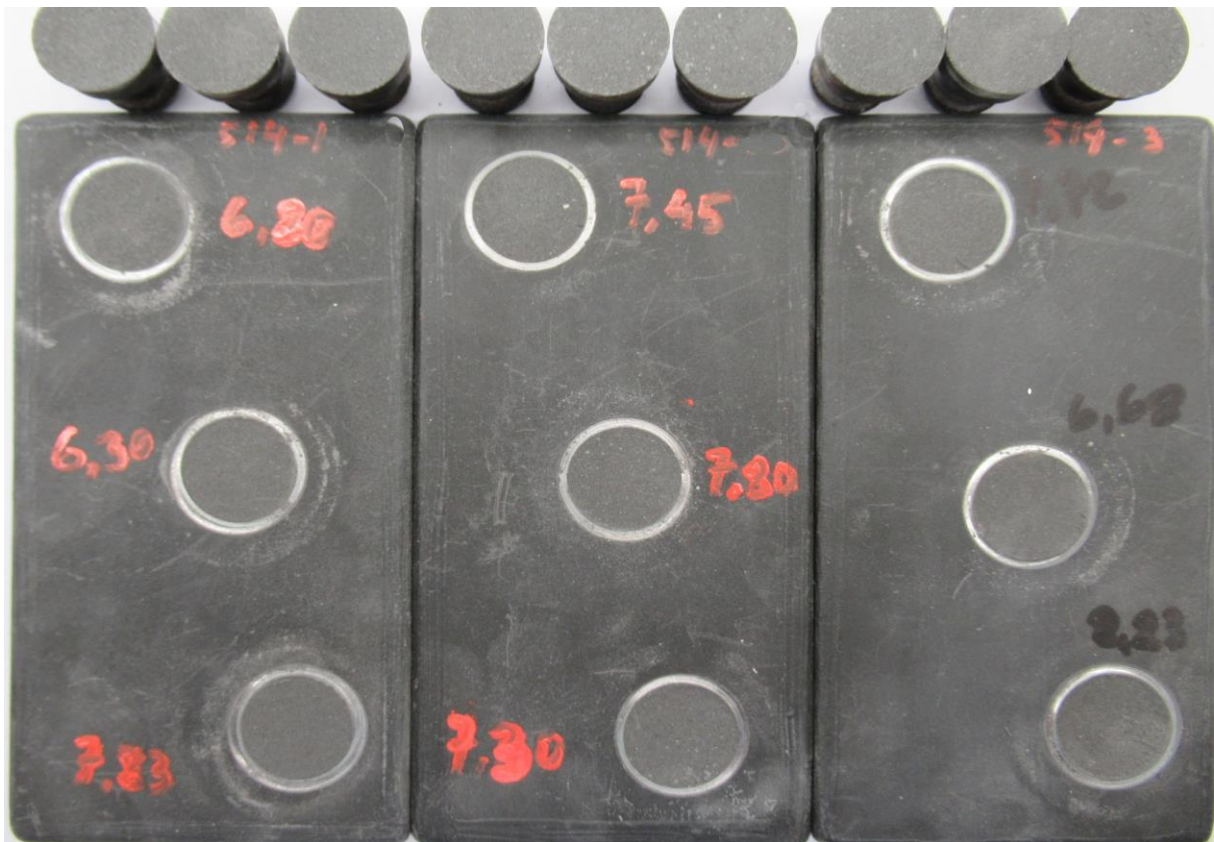


Photo 1: Panels 20/0514-1(1), 20/0514-2(10) and 20/514-3(12) Reference adhesion



Photo 2a: 21/0326-3, 21/0326-3 and 21/0326-5 after 1440 hours Neutral Salt Spray test

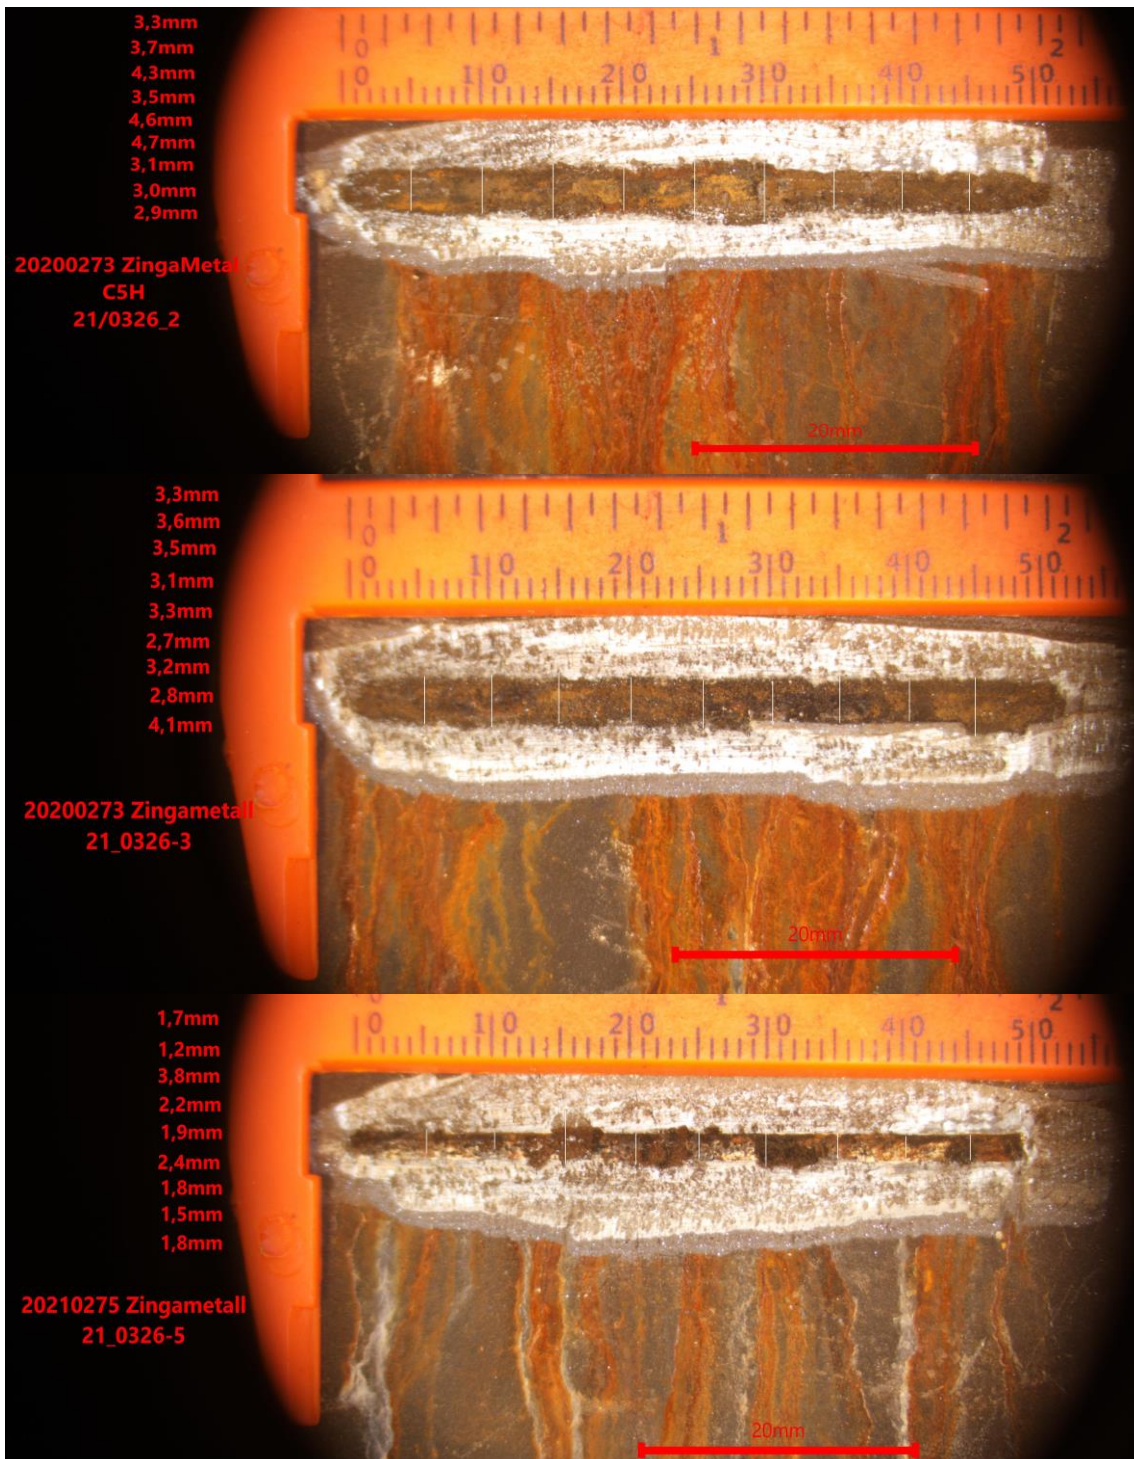

Photos 2b: Detail corrosion creep measurements



Photo 3: Pull off test panel 20/0514-12(14), 20/0514-10(2) and 20/0514-11(8) after 4000 hours Immersion test.